

Observation of new magnetic ground state in frustrated quantum antiferromagnet spin liquid system Cs_2CuCl_4

Hyeong-Jin Kim^{1,2*}, C. R. S. Haines^{1*}, C. Liu¹, Sae Hwan Chun², Kee Hoon Kim², H. T. Yi³, Sang-Wook Cheong³ & Siddharth S. Saxena^{1*}

¹*Quantum Matter group, Cavendish Laboratory, University of Cambridge, Madingley Road, Cambridge CB3 0HE, United Kingdom.*

²*CeNSCMR, Department of Physics and Astronomy, Seoul National University, Seoul 151-747, Republic of Korea.*

³*Department of Physics & Astronomy, Rutgers University, Piscataway, New Jersey 08854, USA.*

Cs_2CuCl_4 is known to possess a quantum spin liquid phase with antiferromagnetic interaction below 2.8 K. We report the observation of a new metastable magnetic phase of the triangular frustrated quantum spin system Cs_2CuCl_4 induced by the application of hydrostatic pressure. We measured the magnetic properties of Cs_2CuCl_4 following the application and release of pressure after 3 days. We observed a previously unknown ordered magnetic phase with a transition temperature of 9 K. Furthermore, the recovered sample with new magnetic ground state possesses an equivalent crystal structure to the uncompressed one with antiferromagnetic quantum spin liquid phase.

Geometrically frustrated spin structures have been the focus of great attention from a broad range of the scientific community due to the potential functional and fundamentally interesting physical properties they display such as superconductivity, magnetism and ferroelectricity [1–6]. The physical properties result from the competition between exchange coupling strengths on the frustrated antiferromagnetic spin lattice. The magnetic phases and phase transitions of frustrated antiferromagnetic quantum spin systems have been investigated experimentally and theoretically [1–8].

In this article, we report the discovery of a new magnetic ground state in the frustrated quantum antiferromagnet spin-1/2 system, Cs_2CuCl_4 , obtained by holding the sample under hydrostatic pressure of approximately 5 kbar at room temperature for 2 days or more. The new phase displays magnetic properties that are similar to chiral helimagnet-like behaviour in stark contrast to the quantum spin liquid phase of unpressurised Cs_2CuCl_4 . Furthermore, there is no significant structural distortion or phase transition accompanying this new magnetic structure.

Cs_2CuCl_4 is a well-studied realization of a two-dimensional quantum spin-liquid phase [10]. The crystal structure of Cs_2CuCl_4 is orthorhombic with space group $Pnma$ [15]. It is composed of CuCl_4^{2-} tetrahedra and Cs^+ ions as shown in figure 1(a). It provides a spatially anisotropic spin-1/2 triangular antiferromagnet, which is characterized by Cu^{2+} ions on a geometrical bc plane. The interchain exchange coupling J' ($= 0.125$ meV) between Cu^{2+} ions along zigzag directions on the triangular bc plane is weaker than the intrachain exchange coupling J ($= 0.375$ meV) along b axis, with the coupling ratio of $J'/J = 0.34$ [10, 16, 17]. Experimentally, the magnetic property of Cs_2CuCl_4 has been assigned to be a two-dimensional quantum spin-liquid phase, by neutron scattering [16 - 18], magnetization [19] and specific heat [20] measurements.

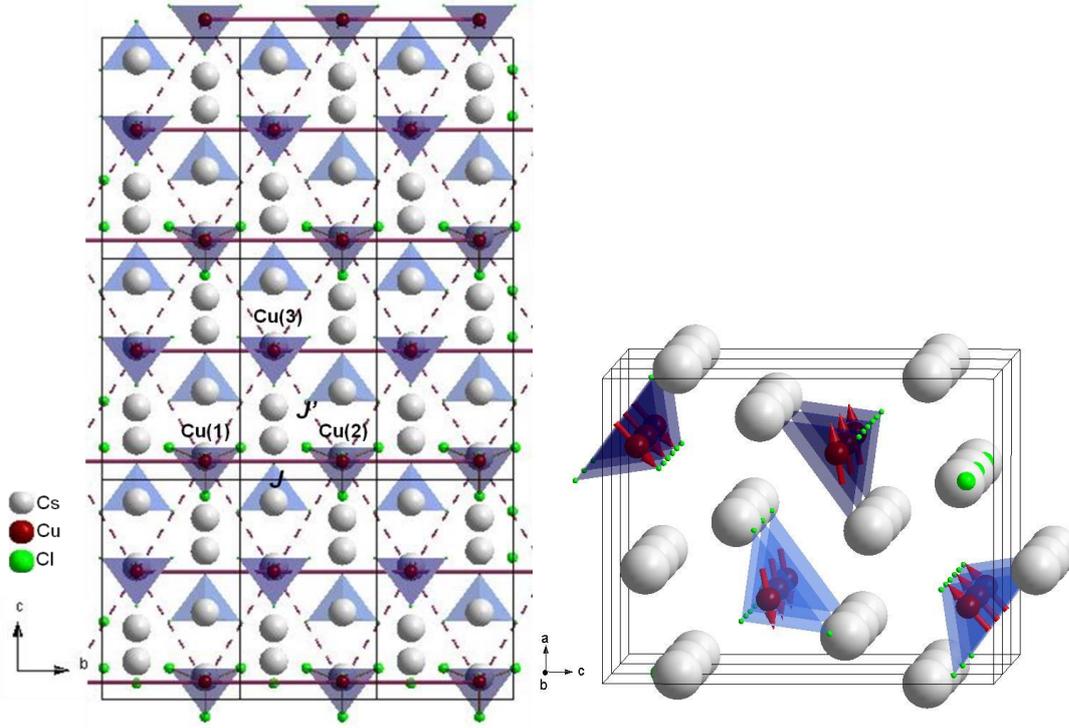


Figure 1: Crystal structure of Cs_2CuCl_4 . (a) Orthorhombic crystal structure for the frustrated quantum antiferromagnet spin-1/2 Cs_2CuCl_4 with Cu^{2+} surrounded by Cl^- ions and Cs^+ . The two antiferromagnetic spin interactions are the nearest neighbour exchange coupling J between Cu(1) and Cu(2) in the b -direction and the next nearest neighbour exchange coupling J' between Cu(1) and Cu(3) on the triangular bc plane with a ratio of $J'/J = 0.34$. (b) spin orientation (grey arrows) in Cu atoms on the ac plane.

The DC magnetic susceptibility of pre-pressurized and post-pressurized Cs_2CuCl_4 is shown in Fig. 2. In the pre-pressurized sample the well-known phase transition from paramagnet to two-dimensional quantum spin-liquid phase with short-range antiferromagnetic order around $T_m = 2.8$ K is observed. We pressurized the sample to 5 kbar for 4 days in a hydrostatic piston cylinder cell and then released the pressure (post-pressurized Cs_2CuCl_4). The susceptibility behaviour of the post-pressurized Cs_2CuCl_4 is significantly different from that of the pre-pressurized sample. The susceptibility is enhanced by nearly an order of magnitude and a new transition is observed at a temperature of $T_s = 9$ K. The post-pressurized phase has a very sharp increase with decreasing temperature to a large maximum moment around $T_s = 9$ K. From fitting the high temperature ($T \geq 20$ K) behaviour using a Curie-Weiss formula $\chi = C/(T + \Theta)$, a Curie temperature of $\Theta = 3.3 \pm 0.6$ K for pre-pressurized Cs_2CuCl_4 was obtained, consistent with the reported value [27], while that of $\Theta = -7.1 \pm 0.3$ K was obtained for the post-pressurized phase. This implies that the spin exchange interaction in Cs_2CuCl_4 changes from antiferromagnetic to ferromagnetic-type after pressurisation. As shown in the upper inset of figure 2, the susceptibility of the post-pressurized Cs_2CuCl_4 exhibits reversible behaviour as field-cooled and zero-field-cooled data are indistinguishable.

In order to investigate the reproducibility and pressurisation time dependence of the new magnetic state in Cs_2CuCl_4 , samples of Cs_2CuCl_4 were pressurized to 5 kbar for increasing amounts of time ranging from 0 to 6 days. The new phase was observed in the samples pressed under about 5 kbar and released after more than two days, as shown in figure 2(b) (solid symbol). Also, in order to verify the stability of the new magnetic phase for the post-pressurized

Cs_2CuCl_4 , we measured its susceptibility after keeping it in an evacuated desiccator for more than one month. We found no change in magnetic properties after this period. This demonstrates that this new magnetic state can be stabilized after a sluggish transition period and is a new magnetic ground state in the triangular frustrated antiferromagnet spin-1/2 system.

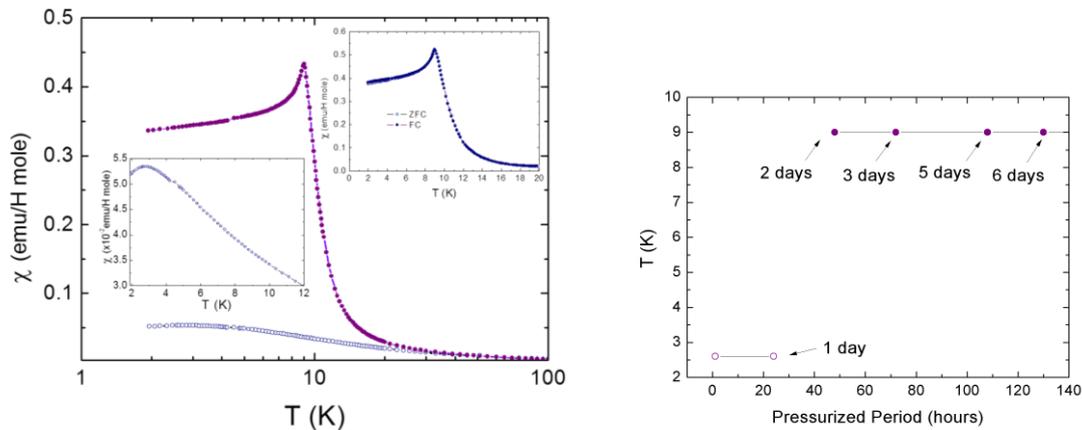


Figure 2: Susceptibility of pre- and post-pressurized Cs_2CuCl_4 with pressing time dependence. (a) The dc susceptibility for pre-pressurized (open symbol) and post-pressurized (solid symbol) Cs_2CuCl_4 with external magnetic field parallel to ac plane under ambient pressure. The susceptibility of the post-pressurized sample shows a transition temperature of $T_s = 9$ K. The upper inset shows that there is no difference between the zero-field-cool and field-cool susceptibilities. (b) The new ground magnetic phase of post-pressurized Cs_2CuCl_4 could be observed under ambient pressure when it was pressed for more than 2 days.

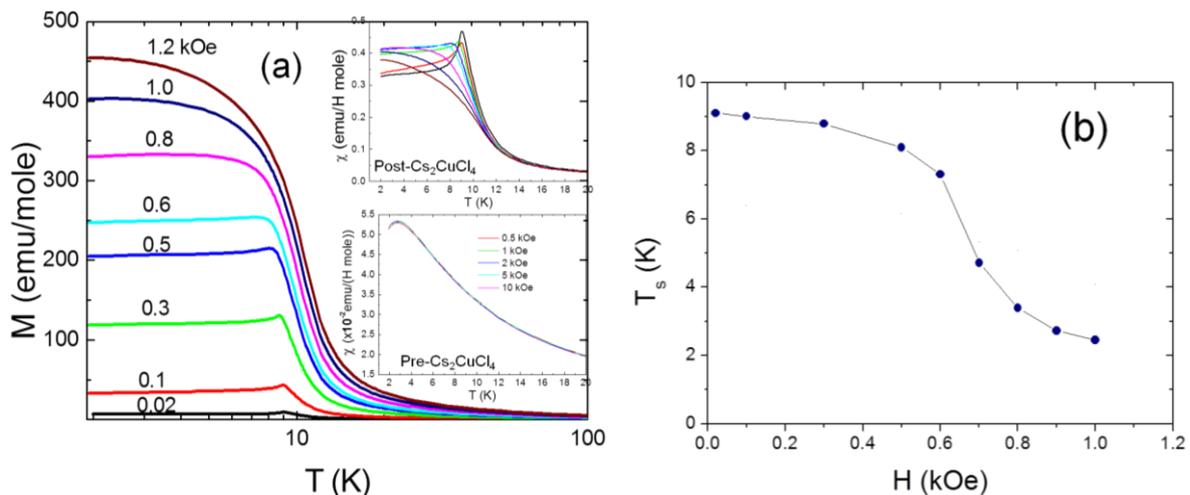


Figure 3: Magnetization of the post-pressurized Cs_2CuCl_4 . Temperature dependence of magnetisation curves of the post-pressurized Cs_2CuCl_4 with each field (parallel to ac plane) from 0.02 to 1.2 kOe under ambient pressure in the main figure (a). The transition temperature is about 9 K up to 0.1 kOe. But as field increase, the peak transition temperature, T_p , is decreased and, above 1 kOe, has disappeared (b). The upper inset in figure (a) shows the susceptibility from the magnetisation curve normalized by each field for the post-pressurized Cs_2CuCl_4 . The lower inset in figure (a) shows the susceptibility of the pre-pressurized Cs_2CuCl_4 without change of transition temperature for several magnetic fields.

Figure 3(a) shows the dc magnetisation curves of post-pressurized Cs_2CuCl_4 as a function of temperature at different magnetic fields parallel to the ac plane. As the applied magnetic field is increased up to 1 kOe, the transition temperature T_s is seen to decrease and broaden, and could not be observed above 2 K at above $H = 1$ kOe as shown in figure 3(b). The magnetization curves show a saturated behaviour above 1 kOe at low temperature, which may suggest a field-induced phase transition to a ferromagnetic order phase. As shown in the lower inset of figure 3(a), these field-dependent susceptibilities, determined from magnetisation data, are also quite different from those for the pre-pressurized Cs_2CuCl_4 which exhibited field-independent susceptibility as shown in the upper inset of figure 3(a).

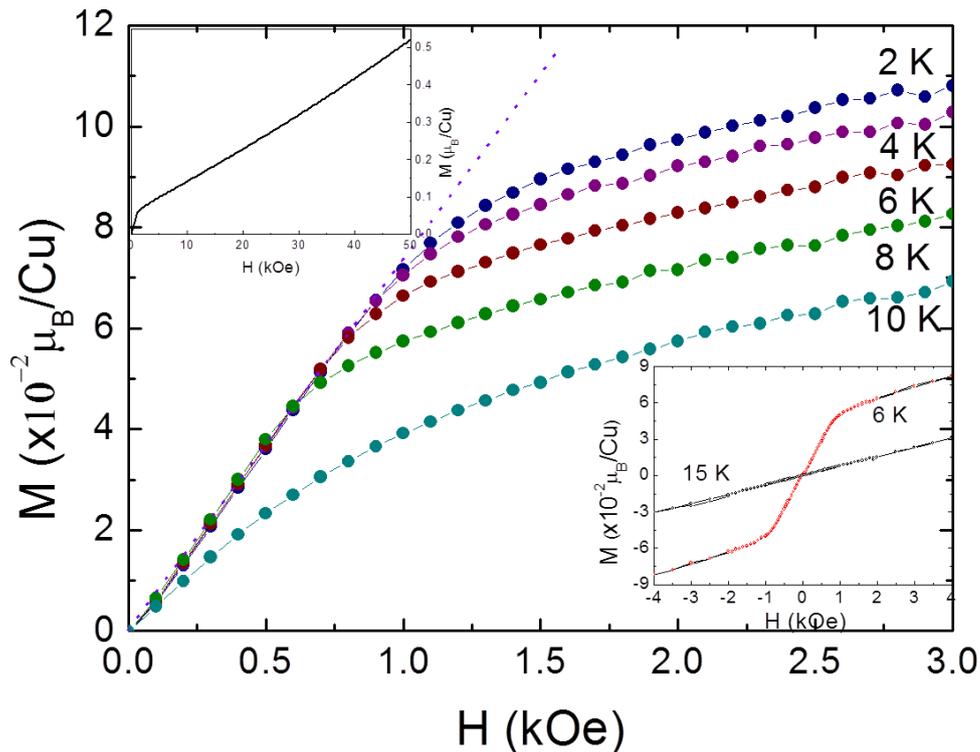


Figure 4: Field dependence of magnetisation for post-pressurized Cs_2CuCl_4 . The field dependence of magnetization of the post-pressurized Cs_2CuCl_4 with each temperature from 2 K, 4 K, 6 K, 8 K and 10 K is shown in the main figure. A possible transition magnetic field H_c could be determined from the deviation of the linear line at low field crossover. As the temperature increases, H_c is decreased and not observed above a transition temperature of 9 K. The magnetization versus field curves shows the S-shape with reversibility and linear behaviour below and above 9 K, respectively, in the lower inset. The upper inset shows the magnetization curve with linear behaviour at 2 K, from 1 kOe to 50 kOe.

While the magnetization versus field curve above the transition temperature of $T_s = 9$ K for post-pressurized Cs_2CuCl_4 is linear, indicating a paramagnetic phase, its curve below 9 K is a reversible S-shape, as shown in the bottom inset of figure 4. Figure 4 depicts the field dependence of magnetization at different temperatures below 10 K. Below $T_s = 9$ K the magnetization curves increase sharply with magnetic field with a universal gradient before slowly saturating above a magnetic field (H_d), which is determined from the point of deviation from the low field susceptibility indicated in the figure. The deviation magnetic field H_d

decreases as temperature increases up to 9 K and could not be observed above 10 K. The magnetic behaviour of the post-pressurized Cs_2CuCl_4 single crystal is similar to that seen in helimagnetic like magnetization curves [38,39], in particular the decrease and disappearance of the transition temperature T_s with increasing field, and of the field H_d with increasing temperature. The magnetisation curve above 1 kOe for post-pressurized version is linearly increased up to 50 kOe, as shown in the upper inset of figure 4. The lack of saturation in the M-H curves may suggest that the field-induced ferromagnetic-type order, shown in figure 3 (a), is based on the disordered antiferromagnetic phase.

The different magnetic properties of pre- and post-pressurized Cs_2CuCl_4 single crystals are likely to be caused by the change of antiferromagnetic spin exchange coupling between Cu ions, caused by structural distortion or structural phase transition. The crystal structure of the pre-pressurized Cs_2CuCl_4 is orthorhombic with lattice parameters of $a = 0.97644(2)$ nm, $b = 0.76143(3)$ nm, and $c = 1.23988(5)$ nm at room temperature as shown in figure 1(a), consistent with the reported results [15]. An X-ray diffraction study under high pressure for a Cs_2CuCl_4 polycrystalline sample reported that the volume and length of all crystallographic directions systematically decreases with increasing pressure up to 40 kbar and are reversible as pressure is released without any structural phase transition [40]. It was reported by P. T Cong et. al, [41] that, in the doped range of $1 \leq \text{Br} \leq 2$ in $\text{Cs}_2\text{CuCl}_{4-x}\text{Br}_x$, the magnetic behaviours are significantly different from spin liquid phase in Cs_2CuCl_4 due to change from O-type orthorhombic (Pnma) to T-type tetragonal (I4/mmm) structure.

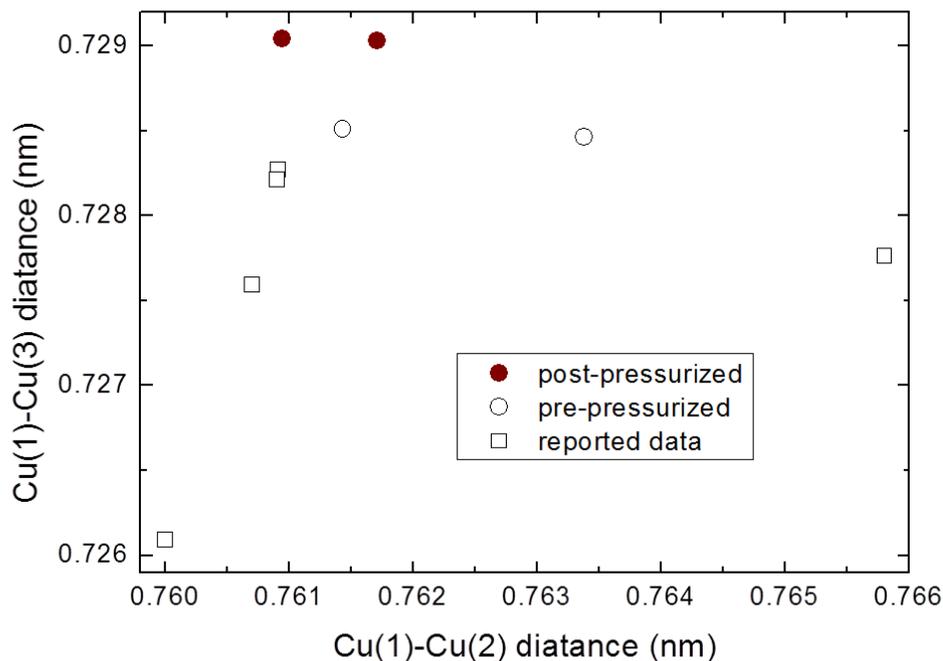


Figure 5: Distances between Cu ions of Cs_2CuCl_4 . The distance between Cu(1) and Cu(3) (related to J') for post-pressurized Cs_2CuCl_4 (solid symbols) is slightly longer than those for pre-pressurized and the reported samples (open symbols) [15, 40, 42-44], however, the other (related to J) is similar to them.

The lattice parameters of the post-pressurized Cs_2CuCl_4 , with the values $a = 0.97663(4)$ nm, $b = 0.76094(3)$ nm, and $c = 1.24146(4)$ nm, are similar to those of pre-pressurized without any crystal structure changes, as shown in Table I. These cell parameters are consistent with the reported x-ray data [15, 40]. While the differences the lengths of a - and b - axis between the pre- and post-pressurized Cs_2CuCl_4 are an order of 10^{-2} %, the differences in the length of c -axis between them could not be ignored with an order of 10^{-1} %. Using our x-ray experiment results, we plot the distances between Cu(1) and Cu(2) ions and between Cu(1) and Cu(3) ions for the pre- and post-pressurized Cs_2CuCl_4 with the reported resulted [15,40, 43-45], as shown in figure 5. While the distance between Cu(1) and Cu(2) of the post-pressurized samples is similar to the pre-pressurized samples and the reported results, the distance between Cu(1) and Cu(3) is slightly longer than them. Due to the slight change between distance of Cu ions, NNN interaction J' on the triangular lattice for the post-pressurized Cs_2CuCl_4 could be changed, relative to the pre-pressurized value ($J' = 0.125$ meV). As a result, it could cause a spin rearrangement on the triangular frustrated antiferromagnet system with a change in spin frustration ratio.

	Pre-pressurized Cs_2CuCl_4 (i)	Post-pressurized Cs_2CuCl_4 (ii)	Difference between (ii) and (i)
a (Å)	9.7644(2)	9.7663(4)	0.0019
b (Å)	7.6143(3)	7.6094(3)	-0.0049
c (Å)	12.3988(5)	12.4146(5)	0.0158
V (Å ³)	921.84(5)	922.6(6)	0.76
Cu(1)-Cu(2)	7.6143(3)	7.6094(3)	-0.0049
Cu(1)-Cu(3)	7.2851(1)	7.2804(6)	0.0053

TABLE I: The comparisons for crystal structures between the pre- and post-pressurized Cs_2CuCl_4 single crystals at room temperature.

As a possible scenario for the interpretation of our results, the magnetic structure for post-pressurized Cs_2CuCl_4 would be considered to be a less frustrated and more quasi-one dimensional antiferromagnet spin-1/2 state with ordered magnetic phase. Theoretical studies suggested that the various ground magnetic phases in Cs_2CuCl_4 might exist as, for example, collinear antiferromagnet, spiral, and dimer phases, which are dependent of J' and second NN chain exchange coupling J_2 [25,28,29]. The magnetic phase of Cs_2CuCl_4 could be sensitive to changes in the interactions of a few percent in magnitude of the largest exchange constant [28] and ferromagnetic couplings in second NN chains are generated by fluctuations [25,28,29]. Tiny structural modification may induce a complete change of the ground state due to the high sensitivity of the exchange coupling constants in the triangular frustrated antiferromagnet spin-1/2 system Cs_2CuCl_4 . We suggest that with pressure treatment the spin liquid gives way to new

magnetic ground state with ferromagnetic-type interactions. In order to explain this phase in post-pressurized Cs_2CuCl_4 , further theoretical as well as experimental study will be required.

Acknowledgments

We would like to thank G. G. Lonzarich, Victor Eremanko, Valentyna Sirenko, S. E. Rowley, P. Nahai Williamson, C. J. Pickard, Patricia L. Alireza, Swee K. Goh and S. E. Dutton for useful discussions. We acknowledge support from KAZATOMPROM Kazakhstan, EPSRC and Jesus College, Cambridge. The work at SNU was supported by National Creative Research Initiative (2010-0018300). Work at Rutgers is funded by the Gordon and Betty Moore Foundation's EPiQS Initiative through Grant GBMF4413 to the Rutgers Center for Emergent Materials. We thank CamCool Research Ltd. for providing the pressure cells used in this work.

Additional information

* Correspondence should be addressed to S. S. Saxena (sss21@cam.ac.uk), H-J. Kim (hjk37@cam.ac.uk) and C. R. S. Haines (crsh2@cam.ac.uk)

References

- [1] Cheong, S. W. & Mostovoy, M. Multiferroic: a magnetic twist for ferroelectricity. *Nature Mater.* **6**, 13 (2007).
- [2] Katsufuji, T. *et al.* Dielectric and magnetic anomalies and spin frustration in hexagonal RMnO_3 ($R=\text{Y, Yb, and Lu}$). *Phys. Rev. B* **64**, 104419 (2001).
- [3] Brühwiler, M. Kazakov, S. M. Ahigadlo, N. D. Karpinski, J. & Batlogg, B. Superconductivity in the geometrically frustrated pyrochlore RbOs_2O_6 . *Phys. Rev. B* **70**, 020503(R) (2004).
- [4] Kawamura, H. Universality of phase transitions of frustrated antiferromagnets. *J. Phys.: Condens. Matter* **10**, 4707 (1998).
- [5] Gardner, J. S. Gingras, M. J. P. & Greedan, J. E. Magnetic pyrochlore oxides. *Rev. Mod. Phys.* **82**, 53 (2010).
- [6] Powell, B. J. & McKenzie, R. H. Quantum frustration in organic Mott insulators: from spin liquids to unconventional superconductors. *Rep. Prog. Phys.* **74**, 056501 (2011).
- [7] Diep, H. T. *Frustrated spin systems* Ch. 2 (World Scientific Publishing Co. 2004).
- [8] Anderson, P. W. Resonating valence bonds: a new kind of insulator? *Mater. Res. Bull.* **8**, 153 (1973).
- [9] Coldea, R. Tennant, D. A. Tsvetik, A. M., & Tylczynski, Z. Experimental realization of a 2D fractional quantum spin liquid. *Phys. Rev. Lett.* **86**, 1335 (2001).
- [10] Morosin, B. & Lingafelter, E. C. The configuration of the tetrachlorocuprate(II) ion. *J. Phys. Chem.* **65**, 50 (1961).
- [11] Coldea, R. *et al.* Neutron scattering study of the magnetic structure of Cs_2CuCl_4 . *J. Phys: Condens. Matter* **8**, 7473 (1996).
- [12] Coldea, R. *et al.* Direct Measurement of the Spin Hamiltonian and Observation of Condensation of Magnons in the 2D Frustrated Quantum Magnet Cs_2CuCl_4 . *Phys. Rev. Lett.* **88**, 137203 (2002).
- [13] Coldea, R. Tennant, D. A. & Tylczynski, Z. Extended scattering continua characteristic of spin fractionalization in the two-dimensional frustrated quantum magnet Cs_2CuCl_4 observed by neutron scattering. *Phys. Rev. B* **68**, 134424 (2003).
- [14] Tokiwa, Y. *et al.* Magnetic phase transitions in the two-dimensional frustrated quantum antiferromagnet Cs_2CuCl_4 . *Phys. Rev. B* **73**, 134414 (2006).
- [15] Radu, T. *et al.* Bose-Einstein condensation of magnons in Cs_2CuCl_4 . *Phys. Rev. Lett.* **95**, 127202 (2005).
- [16] Kohno, M. Quasiparticles of Spatially Anisotropic Triangular Antiferromagnets in a Magnetic Field. *Phys. Rev. Lett.* **103**, 197203 (2009).
- [17] Kousaka, Y. *et al.* Chiral helimagnetism in $\text{T}_{1/3}\text{NbS}_2$ ($\text{T}=\text{Cr and Mn}$). *Nucl. Inst. Meth. Phys. Res. A* **600**, 250 (2009).
- [18] Ghimire, N. J. *et al.* Magnetic phase transition in single crystals of the chiral helimagnet $\text{Cr}_{1/3}\text{NbS}_2$. *Phys. Rev. B* **87**, 104403 (2013).

- [19] Xu, Y. Carlson, S. Söderberg, K. & Norrestam, R. High-pressure studies of Cs_2CuCl_4 and Cs_2CoCl_4 by x-ray diffraction method. *J. Solid State Chem.* **153**, 212 (2000).
- [20] Cong, P. T. *et al.* Structural variations and magnetic properties of the quantum antiferromagnets $\text{Cs}_2\text{CuCl}_{4-x}\text{Br}_x$. *arXiv:1311.3351* (2013).
- [21] Foyevtsova, K. *et al.* Determination of effective microscopic models for the frustrated antiferromagnets Cs_2CuCl_4 and Cs_2CuBr_4 by density functional methods. *Phys. Rev. B* **83**, 125126 (2011).
- [22] McGinney, John A. Cesium Tetrachlorocuprate. Structure, Crystal Forces, and Charge Distribution. *J. Am. Chem. Soc.* **94**, 8046 (1972).
- [23] Helmholtz, L. and Kruh, R. F. The Crystal Structure of Cesium Chlorocuprate, Cs_2CuCl_4 , and the Spectrum of the Chlorocuprate Ion. *J. Am. Chem. Soc.* **74**, 1176 (1952).
- [24] Krüger, N. *et al.* Stable Phases of the $\text{Cs}_2\text{CuCl}_{4-x}\text{Br}_x$ Mixed Systems. *Crystal Growth & Design*, **10**, 4456 (2010).
- [25] Starykh, O. A. & Balents, L. Ordering in Spatially Anisotropic Triangular Antiferromagnets. *Phys. Rev. Lett.* **98**, 077205 (2007).
- [26] Starykh, O. A. Katsura, H. & Balents, L. Extreme sensitivity of a frustrated quantum magnet: Cs_2CuCl_4 . *Phys. Rev. B.* **82**, 014421 (2010).
- [27] Ghamari, S. Kallin, C. Lee, S.-S. & Sørensen E. S. Order in a spatially anisotropic triangular antiferromagnet. *Phys. Rev. B.* **84**, 174415 (2011).